



Biodiesel-Petrodiesel Blends Physicochemical Characterization and Economic Assessment of Designing a Plant in Iran

Omid Koohshekan¹, Alireza Pardakhti¹, Mohammad Ali Zahed², Abozar Salehi¹, Zahra Soltanian Zadeh^{3*}, Amin Mojiri⁴

¹ School of Environment, College of Engineering, University of Tehran, Tehran, Iran.

² Faculty of Biological Sciences, Kharazmi University, Tehran, Iran.

³ Environmental Science & Technology Research center, Department of Environmental Health Engineering, School of Health, Shahid Sadoughi University of Medical Science, Yazd, Iran.

⁴ Department of Civil and Environmental Engineering, Hiroshima University, Japan.

ARTICLE INFO

ORIGINAL ARTICLE

Article History:

Received: 19 October 2022

Accepted: 21 February 2023

*Corresponding Author:

Zahra Soltanian Zadeh

Email:

z.soltanian@ssu.ac.ir

Tel:

+98 2122432040

Keywords:

Environmental Impact,

Biofuel,

Sustainable Development,

Physicochemical Properties,

Economic Analysis.

ABSTRACT

Introduction: By substituting conventional fossil fuels, biofuel can emerge as a potential sustainable energy source with favorable environmental outcomes. Biodiesel, in particular, is increasingly attracting attention due to its high potential to increase the consumption of biofuel and contributing to sustainable development. Experimental studies have revealed that biodiesel can play a considerable role of biodiesel in improving petroleum-based characteristics.

Materials and Methods: Physicochemical properties of pure biodiesel produced through esterification and transesterification, petroleum diesel, and biodiesel-diesel blends were experimentally measured. Ninety percent of the filtered and dried waste cooking oil (WCO) was converted to biodiesel, and it was shown that cetane index, flash point, and fire point increased by applying B10 (10% biodiesel + 90% petrodiesel) instead of petrodiesel.

Results: B10 exhibited an adequate depression in pour point and cloud point by 6°C and 3°C at low temperature, respectively. Also, in this study, an economical study and a sensitivity analysis of a biodiesel production plant from WCO with a capacity of 90 tons per day was carried out, using COMFAR III software. The highest proportion of operating cost belonged to WCO (75%) followed by methanol (10%) and machinery, service, and maintenance expense (5%).

Conclusion: Biodiesel showed a positive influence on petrodiesel characteristics, in which the desired green fuel contributed to save the environment. Eventually, economic analysis provides the possibility of running a plant in Iran as a sustainable solution to energy issues.

Citation: Koohshekan O, Pardakhti A, Zahed MA, et al. *Biodiesel-Petrodiesel Blends Physicochemical Characterization and Economic Assessment of Designing a Plant in Iran*. J Environ Health Sustain Dev. 2023; 8(1): 1897-914.

Introduction

Humans have been dealing with environmental pollution as a major problem in the 21st century^{1,2}. One of the greatest challenges that scientists have faced globally is a gradual increase in conventional fossil-fuel-related pollution and cost, which can be solved by using renewable energy resources^{3,4}.

Various renewable energy sources such as solar energy, wind, biofuels (biodiesel, bioethanol), and waste heat have been developed to efficiently harvest energy⁵⁻⁷. Fossil fuel pollution brings about many detrimental effects on human health, such as exhaust emissions containing particle matters (PM), nitrogen oxides (NO_x), carbon

monoxide (CO) and unburned hydrocarbons (HC), which can cause lung cancer, lung oedema, fatal effects on fetuses, and morbidity promotion⁸⁻¹⁰.

Biodiesel production from waste cooking oil (WCO) is an effective strategy for decreasing the cost of raw material, as well as solving the waste oil disposal problem¹¹⁻¹⁴. It is noticed that low price and availability of waste oil make it more preferable than vegetable oil, either edible or non-edible. High viscosity of the waste oil is the main deterrent to using it directly in combustion systems. Three different methods of thermal cracking, pyrolysis, and trans-esterification have been suggested to reduce viscosity^{15, 16}. Low cost and high conversion efficiency have made trans-esterification more desirable for practical purposes¹⁷.

Several advantages of biodiesel over fossil fuel such as biodegradability, non-toxicity, greenhouse gasses reduction, similarity to petroleum-based diesel structure, and the ability to mix with petrodiesel at different portions are principal reasons for its rising consumption. Moreover, lack of sulfur and aromatics, and less pollution due to the existence of oxygen in its chemical structure turns it into an environmentally friendly fuel^{18, 19}.

Biodiesel contains mono-alkyl ester of a long-chain saturated and unsaturated fatty acids, and its composition consists of 75% C, 13% H, and 12% O by weight, in which the presence of oxygen influences the performance of engine²⁰⁻²². The fewer C-H bonds as a consequence of high concentration of oxygen leads to lower CO and HC emissions. Besides, burning smoothly and high evaporation rate can be counted as the advantages of using biodiesel^{23, 24}. Cloud point and pour point can be considered significant advantages of biodiesel, which improve the cold-flow properties of the fuel²⁵. Therefore, biodiesel has a good potential to use in the transportation sector as an alternative fuel and also in power plants²⁶.

Recently, biodiesel is drawing the attention of south-east Asian countries. In this area, B5 biodiesel blend taken from palm oil is used for transportation as well as power generation and in the industrial sectors. Malaysia is a country that

has reached high levels in biodiesel production by using jatropha and palm oil, and is currently attempting to formulate a richer blend ratio²⁷.

Currently, studies are focused on cheaper feedstock for biodiesel production, such as WCO, waste animal fat, and sewage sludge. Capodaglio and Callegari concluded that waste sewage sludge can be a suitable raw material for biodiesel production, which has a much lower cost by using pyrolysis²⁸. Moecke et al. evaluated economic, environmental and social aspects of biodiesel, reporting that the produced biodiesel can be used as fuel in the artisanal fishing boats. Trans-esterification process was applied for biodiesel production from WCO in a batch reactor with a capacity of 200 (L/day)²⁹. In addition, based on life cycle assessment (LCA) studies, socioeconomic advantages and environmental effects of biodiesel were analyzed using a pilot plant for required processes in order to produce biodiesel from WCO gathered in Brazil³⁰. However, comparing laboratory and large-scale data, LCA studies have provided good information on the cultivation and harvesting of algae. Results have demonstrated favorable environmental outcomes regarding particulate matter, global warming, and total NO_x and SO_x emissions³¹.

In Iran, replacing conventional fuel with renewable energy from biomass sources such as citrus waste products gives a higher benefit and has a great potential for biodiesel production, bioethanol, and biogas^{32, 33}. It should also be noted that biodiesel production has been studied technically and economically by authors in Iran, who considered waste oil to be an affordable resource³⁴⁻³⁷.

Biofuel has great potential in Iran, since about 7% of the territory is covered with forests, which can produce valuable resources such as lipids. Algae, fish oil, as well as plant oil sources such as jatropha, castor plant, and palm. These are suitable sources for biodiesel production, especially WCO, of which 0.3 million tons is produced annually. Therefore, this appealing setting provides strong evidence that it is quite enough to forecast blending ratios up to B10 by 2026³⁸.

China, USA, India, and Russia are the leading CO₂ producers in the world³⁹. Iran emitted 3.6 tons CO₂ per capita in 1990, which reached 5.3 tons in 2000. This amount of pollution rate has grown in recent years to reach 7.56 tons per capita in 2015⁴⁰.

The objective of this study is to evaluate the specification of WCO methyl ester (biodiesel, B100) and conventional petrodiesel fuel (B0) as well as biodiesel blends. WCO as a low-cost raw material was used experimentally to produce biodiesel. Moreover, B10 in Iran, as an alternative to petrodiesel, is anticipated to be highly promoted by 2035. Due to its enormous potential to expand the consumption of biofuel and contribute to sustainable development, biodiesel is gaining more and more attention. Moreover, a factory with a capacity of 90 tons per day was examined economically.

Materials and Methods

Methodology

WCO was obtained from several local restaurants and then mixed in order to make feedstock for biodiesel production process. Figure 1 shows the biodiesel production apparatus for both esterification and trans-esterification, which consists of 6 items. The pilot of desired reaction process was equipped with a reflux condenser, 500 ml three-necked flask, heater stirrer, magnetic stirrer, water bath, and a thermometer. The reagents applied in the experiment conditions of biodiesel production are presented in Table 1. The yield of fatty acid methyl ester (FAME) was calculated by equation (1), which is mentioned below⁴¹:

$$\text{yield (\%)} = \frac{[\text{weight of biodiesel (g)}]}{[\text{weight of lipid (g)}]} \times 100 \quad (1)$$

Biodiesel production

Biodiesel production process is performed in four steps:

1. Waste oil filtering and preparation

Gathered waste oil needs an impurity separation process. To this end, as shown in Figure 2 (a), suspended food particles should be separated by filtering through filter paper. Absence of water results in the prevention of soap production, which

is undesirable for biodiesel production. The reaction of water and alcohol reduces process yield and makes the final separation difficult. Hence, it was placed on a hot plate at a temperature above 100 °C stirring for an hour to eliminate water content in the waste oil.

2. Esterification and transesterification reactions

Heating oil decomposes the long carbon chain to create free fatty acids⁴². The reaction of free fatty acids with alkali catalyst produces soap, and water which decreases the outcome of reaction and forms the emulsion^{43,44}. An acid-catalyzed technique was used in biodiesel production to decrease the content of free fatty acid (FFA) to less than 1% in order to convert FFA into methyl ester until WCO was prepared for the trans-esterification process by base-catalyst⁴⁵⁻⁴⁷. A titrimetric method was applied to determine the FFA content representing an amount of 5.37 wt. %. In the acid-catalyzed process, 100 ml filtered oil with 8:1 molar ratio of methanol (purity 98%) to oil and 1% (v/v) of H₂SO₄ (98%) were applied to the crude oil. As shown in Figure 2 (b), the reaction was carried out at 75 °C and 800 rpm. After 2 hours, a separating funnel was used to separate the acid, impurity, and methanol. After 10 hours, the lower layer (esterified oil) was separated and entered into a rotary evaporator. It can eliminate almost all water and alcohol excess after 1 hour. Then, to perform transesterification reaction, processed waste oil (at 50 °C) again was poured into three neck-round flasks equipped with a reflux condenser and a thermometer (Digital thermometer (KT-300) 240x30x30 mm, accuracy -50 to 300 Celsius) to avoid alcohol vaporization, then a combination of 25 ml of methanol and 0.5% w/w (of oil) sodium hydroxide (99%) was added to the flask. The reaction was allowed to proceed at 70 °C (± 2) with continuous stirring at 600 rpm for 1.5 hours and refluxing by a water-cooled condenser. According to the color change and return of alcohol from the condenser in the first 45 minutes, it seems that most of the conversions took place in this period.

3. Separation of biodiesel and glycerol:

When the reaction was complete, the mixture

was passed through to the separating funnel for a day to separate the rich phase of glycerol from biodiesel. There might be some excess impurities in the lower layer which has to be removed. It can be seen in Figure 2 (c).

4. Post-treatment process

It was probable that the biodiesel still contains glycerol, alcohol, and impurities. Therefore, as shown in Figure 2 (d), the sample was heated up to 75 °C with continuous stirring for half an hour to

vaporize alcohol, and then it was washed with warm distilled water at least three times until the outlet water became slightly clear. In the next stage, excess water and methanol were eliminated by a rotary evaporator. Finally, the remaining water was taken from biodiesel by heating and using granular Na_2SO_4 . Eventually, a filter paper (150 mm diameter, no.1) was employed to filter the final product which was prepared for blending with ordinary diesel.

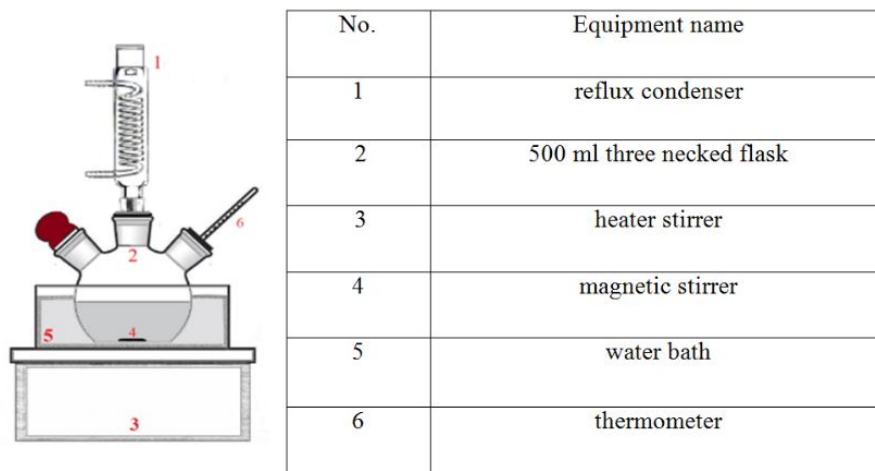


Figure 1: Schematic diagram of biodiesel production setup

Table 1: Summary of processes of biodiesel production from WCO

| | Parameter | | Specification |
|----------------------|----------------|---------------------|--|
| | Esterification | Transesterification | |
| Source | WCO | | |
| Alcohol used | Methanol | | 98 % purification Merck |
| Catalyst used | H_2SO_4 | NaOH | Acidic catalyst: 98% Alkali catalyst: 99% |
| Reaction temperature | 75 °C | 70 °C | - |
| Reaction time | 2 h | 1.5 h | - |
| Stirring speed | 800 rpm | 600 rpm | - |

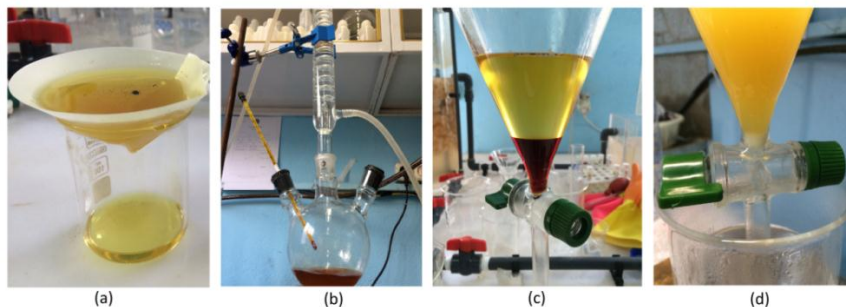


Figure 2: (a) Waste oil filtering, (b) Reaction system, (c) Separating funnel, and (d) Purification

Blending of biodiesel

It is not common to use neat biodiesel because of economic disadvantages, incompatibility with engines, and physicochemical issues, such as low energy content, oxidation stability, higher kinematic viscosity, and density. Petro-diesel can be completely miscible to biodiesel at different portions^{48, 49}. Biodiesel blend at different ratios is a suitable choice to improve the quality of conventional petrodiesel. Therefore, these blends were supplied to verify the effect of blending on petrodiesel based on ASTM D6751 standard procedure.

Petro-diesel was prepared from Tehran refinery based on Euro 5 standard. In order to make blends at three different ratios including B5, B10, and B20 by volume fraction, they were mixed under following appropriate conditions and are shown in Figure 3. To make these blends, a 500 ml neck-round flask was used and biodiesel was added to petroleum-based diesel at 45 °C. The flask was fixed with a clamp on a vertical stand with continuous stirring at a speed of 700 rpm for 1 hour.

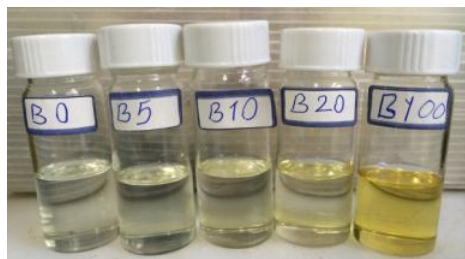


Figure 3: Biodiesel Blends: B0, B5, B10, B20, and B100

Physicochemical analysis

Physical and chemical characteristics of biodiesel and biodiesel/petro-diesel blends were

analyzed using ASTM D6751 method.

Economic analysis

The production steps of biodiesel on a laboratory scale and chemical parameters in its characteristics are described in the previous section. Then, a WCO biodiesel plant was evaluated economically with a capacity of 90 tons per day. Economic estimates of factory construction and internal rate of return (IRR) sensitivity analysis were performed by COMFAR III software on a variety of parameters.

COMFAR software has been designed by the United Nations Industrial Development Organization (UNIDO) to evaluate economic projects. The software makes it easy to organize and calculate financial reports. The advantages of COMFAR software include high flexibility, user-friendliness, low error, and high level of sensitivity.

Results

Characterization of fuel properties

The percentage of biodiesel yield (lipid conversion efficiency) obtained from optimum reactions was 90% after eliminating glycerol from separating funnel. Table 2(a), (b) shows the properties of produced biodiesel (B100) in comparison to other studies and demonstrates the chemical and physical properties of the blends such as kinematic viscosity at 40 °C, density, pour point, cloud point, flash point, fire point, sulfur content, cetan index, and calorific value. These results are in accordance to the standard test method ASTM D6751, and the data depicted in Table 2 are expressed as an average of three values in each test.

Table 2(a): Biodiesel obtained from WCO characterization

| Properties | Unit | Test method | ASTM-BD D6751 | N. Yilmaz et al. ⁵⁰ | Z. Al-Hamamre, A. Al-Salaymeh ⁵¹ | A.N. Phan, T.M. Phan ⁵² | Sadaf et al. ⁵³ | Produced Biodiesel (this study) |
|------------------------------|--------------------|-------------|---------------|--------------------------------|---|------------------------------------|----------------------------|---------------------------------|
| Kinematic viscosity at 40 °C | mm ² /s | D445 | 1.9 - 6.0 | 4.57 | 5.86 | 4.89 | 5.83 | 5.8 |
| Density at 15 °C | kg/m ³ | D4052 | 860 to 900 | 855 | 877 | 880 | 874 | 870 |
| Pour point | °C | D97 | -15 to 10 | | | 0 | 1 | 9 |
| Cloud point | °C | D2500 | | | | 3 | 10.5 | 21 |
| Flash point | °C | D93 | 130 min | 126 | 150 | 120 | | 144 |
| Fire point | °C | D92 | | | | | | 198 |
| Cetan index | | D976 | | | | | | 59.7 |
| Sulfur content | ppm | D4294 | 15 ppm | | | | | 12 |
| Calorific value (HHV) | MJ/kg | D240 | > 35 | 40.5 | 35.66 | 41.84 | 37.2 | 45.11 |

Table 2(b): Physicochemical fuel properties of biodiesel in comparison to petrodiesel and its blends

| Properties | Unit | Test method | B0 (Petrodiesel) | B5 (5 % v/v) | B10 (10 % v/v) | B20 (20 % v/v) | B100 (Biodiesel) |
|------------------------------|--------------------|-------------|------------------|--------------|----------------|----------------|------------------|
| Kinematic viscosity at 40 °C | mm ² /s | D445 | 2.75 | 2.83 | 3.04 | 3.1 | 5.8 |
| Density at 15 °C | kg/m ³ | D4052 | 821 | 823 | 827 | 834 | 870 |
| Pour point | °C | D97 | -6 | -8 | -12 | -12 | 9 |
| Cloud point | °C | D2500 | 2 | 0 | -1 | -2 | 21 |
| Flash point | °C | D93 | 63 | 63.5 | 64.5 | 66 | 144 |
| Fire point | °C | D92 | 91 | 92 | 93 | 94.5 | 198 |
| Cetan index | | D976 | 55.9 | 56.1 | 56.4 | 57.1 | 59.7 |
| Sulfur content | ppm | D4294 | 56 | 55 | 52 | 48 | 12 |
| Calorific value (HHV) | MJ/kg | D240 | 45.98 | 45.91 | 45.89 | 45.79 | 45.11 |

Fuel properties analysis

The following section discusses the properties of blending pure biodiesel with conventional petroleum-based diesel.

Density

Density is an important property of fuel atomization and affects the energy content, air-fuel ratio within the diesel engine and cetan number^{54, 55}. Figure 4 presents the variation in density with volumetric percentage of biodiesel-petro diesel. The foregoing density for petro-diesel goes up from 821 to 823, 827, and 834 (kg/m³) for B0, B5, B10, and B20, respectively. Thus, it can be seen that blend density increased slightly by increasing the biodiesel percentage.

Kinematic viscosity at 40 °C

One of the fuel properties affecting the fuel

injection system is kinematic viscosity. Fuel fluidity and atomization are important characteristics of fuels measured by kinematic viscosity^{56, 57}. Unsuitable fuel injection and pumping can cause incompetency at low temperatures due to higher kinematic viscosity⁵⁸. The kinematic viscosity of biodiesel was measured at 5.8 (mm²/s), and the recommended range of kinematic viscosity is 1.9- 6.0 (mm²/s) according to ASTM test method⁵⁷. It was observed experimentally that the kinematic viscosity at 40 °C of petro-diesel increased when the biodiesel portions in petro-diesel rose (Figure 4). The kinematic viscosity changed from 2.75(B0) to 2.83, 3.04, and 3.10 (mm²/s) for B5, B10, and B20, respectively.

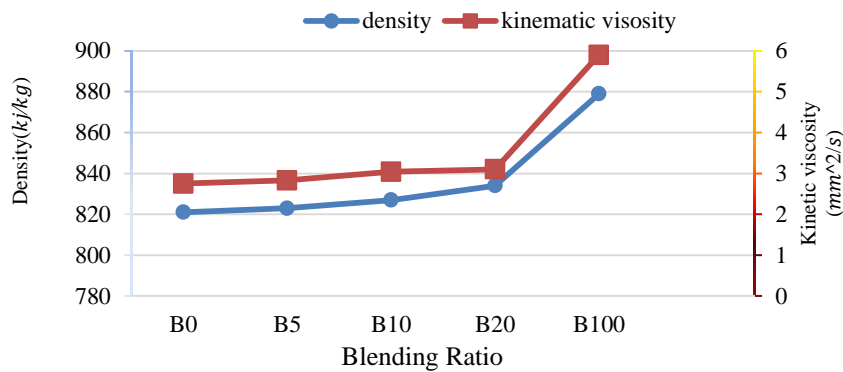


Figure 4: Density and kinematic viscosity of blends

Calorific value (MJ/kg)

The energy content of biodiesel is known as the potential energy contained in a given biodiesel fuel influencing the engine power, which depends on the energy content of the oil as a feedstock^{42, 59}. In this investigation, the energy content known as higher heating value (HHV) of methyl ester was measured and the results are presented in Table 2. Figure 5 shows blended biodiesel energy is slightly less than petrodiesel. An increase in biodiesel-diesel blend ratios marginally decreased the calorific value of the blends. The calorific value of the biodiesel was

measured 45.115 (MJ/kg) which was 98.11 % of the petro-diesel (B0) and the energy quantity of B5, B10, and B20 were found 0.13%, 0.18%, and 0.4% less than petro-diesel, respectively, as reported in Table 2(b). Therefore, considering the final cost of biodiesel blends, HHV is an important characteristic of a fuel, which indicates the upper limit of the available thermal energy produced by a complete combustion of fuel. It may not be reasonable to mix higher amounts of biodiesel to maintain the adequate expected energy content; therefore, B0 to B10 would be logical options.

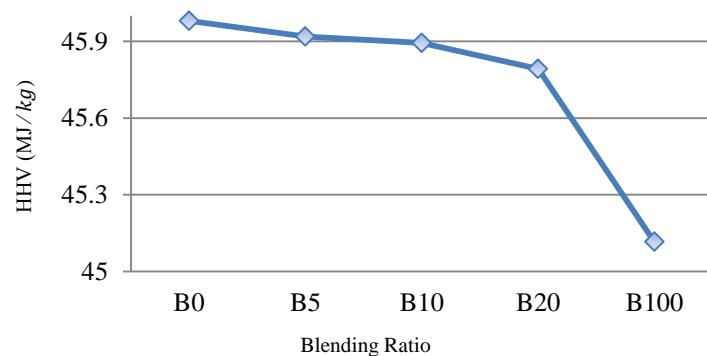


Figure 5: Calorific value (HHV) of biodiesel blends

Cetane index

In another experimental investigation, cetane value of fuel was evaluated to measure the ignition quality. The ignition delay time is the period that fuel is injected and began to combust. During this time the fuel evaporates and is dispersed with the compressed air in the combustion chamber. If all conditions are available, the fuel will spontaneously begin to combust. The ignition time

depends on the composition of the fuel, operational parameter, and engine design. Cetane is the speed of fuel combustion and an indicator of fuel quality. The lower cetane values have a longer ignition delay compared to the higher ones. Cetane index is an essential property since biodiesel affects the petrodiesel cetane index. The recommended cetane index range for biodiesel/petrodiesel blends is at least 40⁶⁰. In this study, B0 cetane index was found

55.9 and attained 56.1, 56.4, and 57.1 for B5, B10, and B20, respectively (Table 2 and Figure 6).

Sulfur content

Due to the lower sulfur content in biodiesel compared to petrodiesel, lower amount of SO₂ is produced⁶¹. Sulfur content of diesel fuel depends on fuel types and varies from one engine to another. Sulfur is known as an emission causing acid rain, and affects PM emissions to the extent that has convinced the scientists to limit diesel sulfur content more than ever. Sulfur subtraction needs to be taken into account because it can increase ecosystem damage and cause lots of

losses in the country. As a result, new technologies of emission control and heavy processing have been performed at Tehran refinery to reduce sulfur content in recent years.

The biodiesel sulfur content was measured 12 ppm, while the proposed value of the sulfur-based fuel on ASTM D6751 standard is reported less than 15 ppm⁶². The results show that biodiesel as an additive can reduce the sulfur content of petrodiesel from 56 ppm (B0) to 52 ppm (B10). Sulfur content reduction trend is given in Table 2 and it can be seen in Figure 6.

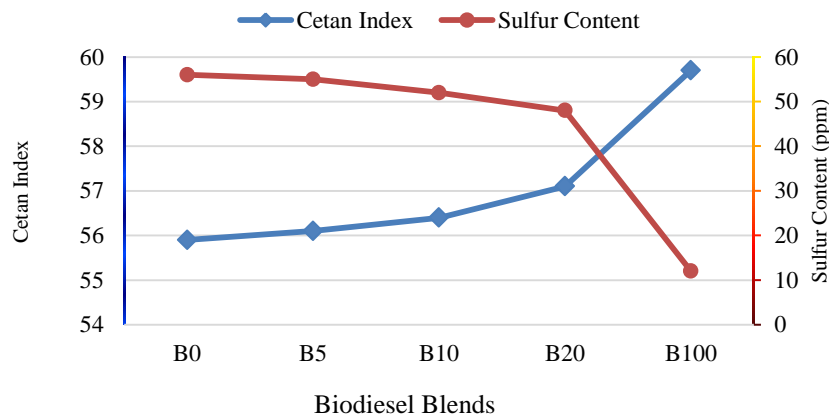


Figure 6: Cetan index and sulfur content of biodiesel blends

Flash point and Fire point (°C)

The flash point shows the minimum temperature at which fuel vaporizes enough to get ignited, and is known as the safety measure of fuels for transportation and storage. The fire point is the lowest temperature at which the vapor of fuel continues to burn for at least 5 seconds after ignition^{63, 64}. Table 2 demonstrates a slight increase in several percentages of biodiesel in the blends and a drastic two-fold rise in 100% biodiesel compared to ordinary fuel. The flash point and fire point of petrodiesel were measured 63 and 91°C, respectively. Figure 7 demonstrates

that the flash point and fire point increase as the blend ratios increase. The flash point of 100% biodiesel complied with ASTM D6751, and it had the highest flash point indicating low volatility of this fuel⁶⁵. Mixing biodiesel with petro-diesel can increase the flash point of the blends and is a suitable choice in terms of safety, since higher flash point of biodiesel decreases flammability hazard providing more safety in transferring and shipping. So, increasing the rate of biodiesel positively enhances the safety regulation of introduced fuel.

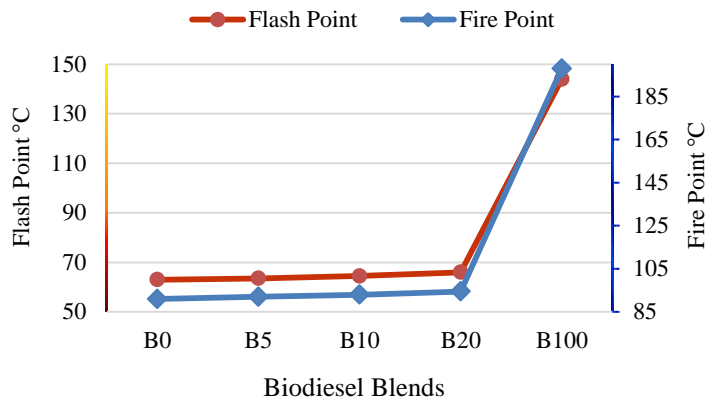


Figure 7: Flash point and fire point of biodiesel blends

Pour point and cloud point (°C)

Fuel constraints under cold weather are generally determined by factors such as cloud point, pour point, and cold filter plugging point. Cloud point shows the temperature at which the cluster of wax crystal can be seen, and the temperature at which fuel flow reduces due to gel formation during fuel cooling is known as the pour point of fuels⁶⁶. The pour point and cloud point of WCO methyl ester were measured at different mixing portions as represented in Figure 8 and

Table 2. Biodiesel (B100) had a higher pour point and cloud point in comparison with petrodiesel (B0), 9°C, and 21°C, respectively. It is important to notice that biodiesel can decrease these characteristics by making blends; in other words, both cloud point and pour point of biodiesel blends were lower than conventional petrodiesel. According to Table 2, B10 had lower pour point and cloud point than petro-diesel enabling higher compatibility with vehicles.

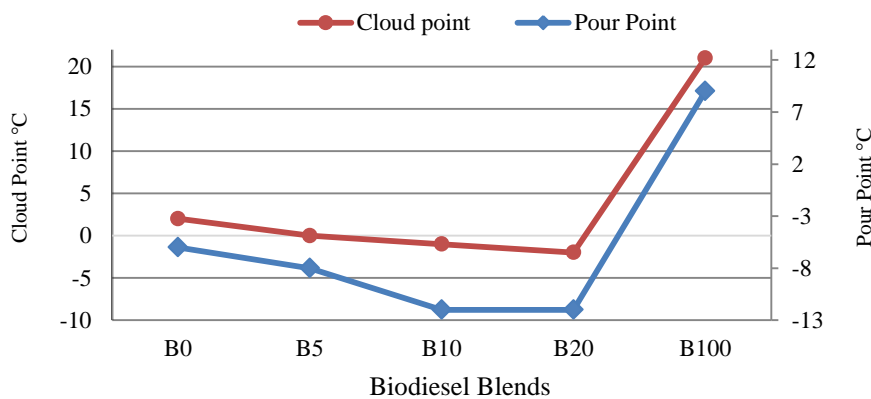


Figure 8: Pour point and cloud point of biodiesel blends

Distillation curve (°C)

Fuel tendency to form smoke and soot is evaluated by distillation curve⁶⁷. Fuel distillation significantly impacts fuel safety and performance, since volatility has a profound effect on fuel tendency to vaporize, especially initial boiling point (IBP), which influences fuel vapor pressure⁶⁸. According to Table 3 and Figure 9, the

distillation curve is the temperature change as a function of distillation percentage from IBP to final boiling point (FBP), performed at the atmospheric pressure of fuel.

In this survey, ASTM D86 was used for obtaining experimental distillation, because at different percentages of recovery, biodiesel has the highest distillation temperature. The obtained

results showed that the percentage of biodiesel had direct relationship with IBP and FBP. The IBP of biodiesel was measured at 261 °C, while conventional diesel had the lowest value of 175 °C. IBP was measured at 170.5, 171, and 172 °C for B5, B10, and B20, respectively. According to

Table 3, boiling point at 10% to 95% recovery of each sample was higher in contrast to petrodiesel (B0). It can be demonstrated that at the IBP and FBP the samples temperatures converge, while they diverge as they reach an equal content of each fuel in blends.

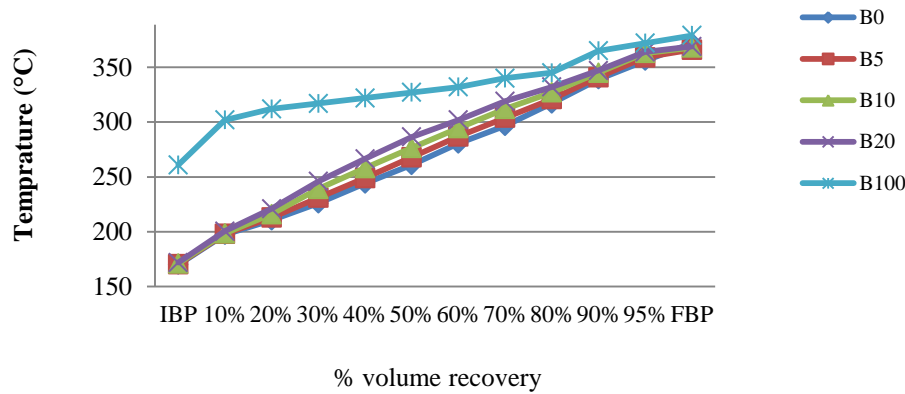


Figure 9: Distillation curve of biodiesel, diesel, and the blends

Table 3: Distillation temperature for biodiesel, petrodiesel, and the blends

| Vol. % | B0 | B5 | B10 | B20 | B100 |
|--------|-------|-------|-------|-------|------|
| IBP* | 170 | 170.5 | 171 | 172 | 261 |
| 10 | 197.4 | 198 | 198.5 | 200.5 | 302 |
| 20 | 210.5 | 213 | 216 | 221 | 312 |
| 30 | 226 | 231 | 239 | 246 | 317 |
| 40 | 244 | 249 | 258 | 266.5 | 322 |
| 50 | 261 | 268 | 276.5 | 286.5 | 327 |
| 60 | 280.5 | 287 | 294.5 | 302 | 332 |
| 70 | 296.5 | 304 | 312 | 319 | 340 |
| 80 | 317 | 321 | 327 | 332 | 345 |
| 90 | 339 | 341 | 345 | 347 | 365 |
| 95 | 356 | 359 | 363 | 364 | 372 |
| FBP** | 372 | 366 | 368 | 369 | 379 |

* Initial Boiling Point
 ** Final Boiling Point

Economic assessment of biodiesel production

From an economic viewpoint, WCO is the best raw material in contrast to the utilization of imported fresh edible oil, when only 10-15% of consumed edible oil in Iran is produced by domestic production and the rest is imported⁶⁹. It is not reasonable to neglect this large amount of purchased edible oil. According to results, biodiesel production includes the expenses of raw materials, energy, human labor, services, and maintenance.

Not only would the daily consumption of 80

million liters of petrodiesel in Iran be reduced by 10%, but also it can be replaced by an alternative fuel. Therefore, biodiesel would potentially own an 8 million liter market per day. Regarding the capacity of producing biodiesel from WCO, B10 can be produced in order to be consumed in big cities that are receiving the most exposure to pollution (Tehran, Mashhad, Karaj, Esfahan, Shiraz, etc.). For instance, the amount of WCO in Tehran has come to 60000 kg per day only by the food service industry and food manufacturing. As a result, this amount of waste oil is an indigenous

threat to ecosystem of Tehran. Regarding the potential of Tehran as a sources of raw material and operationalization, this city can be a suitable option for launching biofuel production. Therefore, B10 is anticipated to be highly promoted as a substitute for petrodiesel by the year 2035 in Iran.

For the economic evaluation, a discount rate of 18% (tax rate = 9%) was assumed for the survey. According to oil conversion efficiency to biodiesel of 90% and biodiesel density of 870kg/m³, the annual increase rate of operating costs, the annual increase rate of biodiesel price, and the annual increase rate of glycerol price were considered 17%, 2%, and 17% respectively, as inputs to the COMFAR III software. Operational costs and distribution expenses of biodiesel production from WCO are presented in Table 4 and Figure 10, respectively. According to Table 4, unit cost of biodiesel production in Iran is anticipated to be

0.412\$/L. Figure 10 indicates that the highest share of expenses belongs to WCO (75%), followed by methanol (10%), machinery, services, and maintenance (5%). Moreover, Table 5 shows the total investment costs, and Table 6 demonstrates the revenues from the sale of biodiesel and glycerol. As shown in Figure 11, the largest share of total investment costs belongs to process equipment (62 %), followed by contingencies fees (15%) and utility (9%), respectively. According to economic calculations performed by COMFAR III software, Net Present Value (NPV) of Total Capital Invested (at 18%) was obtained 11,722,000 \$, and the IRR on investment was assessed 20.21 % with a 5-year normal payback. Overall, positive net present value (NPV) (\$11,722,000) and IRR indexes of more than 18% (21.20 %) can be found, which indicates that the process would be financially feasible.

Table 4: Operating costs for a 90 t/d WCO-biodiesel plant

| Item | Unit | Price (\$/unit) | Quantity | Total cost (\$) |
|---|-------------------------|------------------|----------|-----------------|
| Direct Costs | | | | |
| WCO ^a | Tone | 300 ^b | 33000 | 9900000 |
| Methanol ^a | Tone | 215 | 6005 | 1291075 |
| H ₂ SO ₄ ^a | Tone | 270 | 341.2 | 92129 |
| NaOH ^a | Tone | 1370 | 37.95 | 51991 |
| H ₂ O ^a | M ³ | 0.18 | 39930 | 7187 |
| Electricity ^a | Kwh | 0.07 | 1724910 | 120744 |
| Machinery, service and maintenance (10% of process equipment utility structure) | equipment, building and | | | 676900 |
| Royalty | | | | 425000 |
| Labor ^c | Person | 9240 | 9 | 83160 |
| Depreciation | | | | 486554 |
| Total direct costs | | | | 13134740 |
| Indirect costs | | | | |
| Insurance | | | | 88160 |
| Marketing (2% of total revenue from biodiesel and crude glycerol sale) | | | | 837390 |
| Total indirect costs | | | | 925550 |
| Total operating costs | | | | 14060290 |
| Unit cost of biodiesel production | | | | 0.412\$/L |

^a All given prices are based on Iran market data (2020 April).

^b 25 % of fresh vegetable oil price.

^c Including basal labor payment and other expenses based on Iran ministry of labor laws.

Table 5: Total capital cost for a 90 t/d WCO-biodiesel plant

| Item | Cost (Thousand USD) |
|-------------------------------------|---------------------|
| Equipment | |
| Process equipment ^a | 5198 |
| Utility equipment | 806 |
| Total equipment cost | 6004 |
| Civil and construction ^a | |
| Land acquisition | 55 |
| Building and structure | 161 |
| Total civil cost | 216 |
| Installation ^b | 600 |
| Contingencies fee ^c | 1283 |
| Pre-production expenditures | 302 |
| Total capital cost | 8405 |

a All given prices are based on Iran market data – 2020 April.

b 10% of equipment costs including engineering design cost, construction labor, piping, electrical. and control instruments and their programing and other expenses.

c 18% of total equipment cost and civil and construction cost (except land expense)

Table 6: Total revenue from crude biodiesel and glycerol sales

| Quantity (tone) | Price (\$/ton) | Sale(\$) |
|------------------|----------------|----------|
| Biodiesel: 29700 | 1065/8 | 31654260 |
| Glycerol: 4300 | 240 | 1032000 |

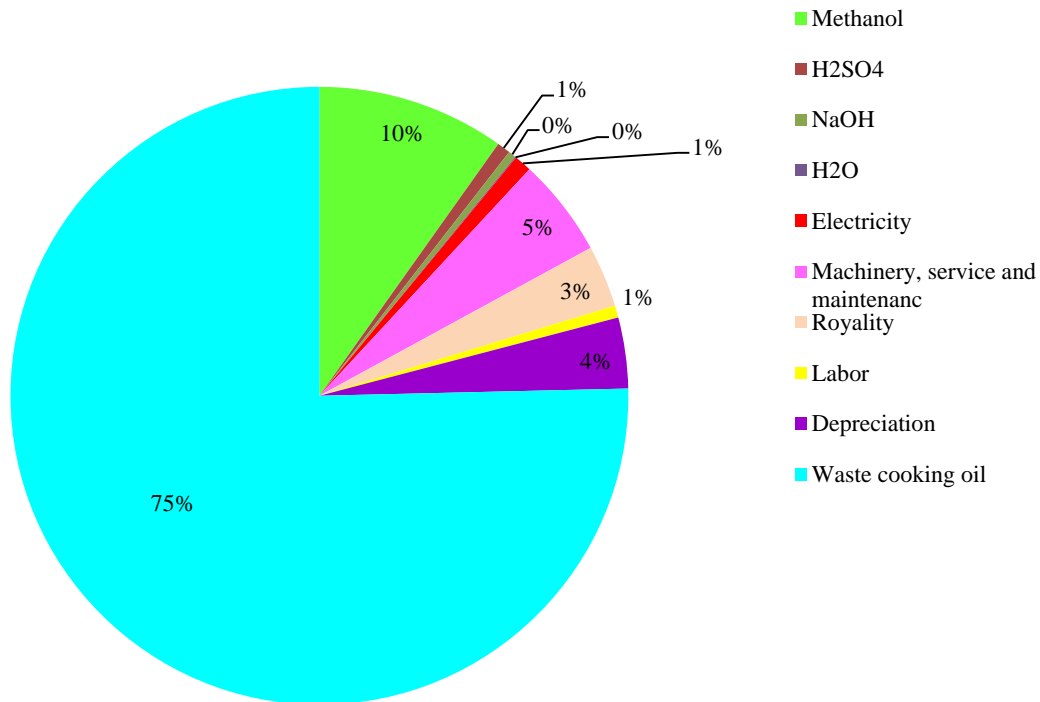


Figure 10: Distribution of expenses in biodiesel production

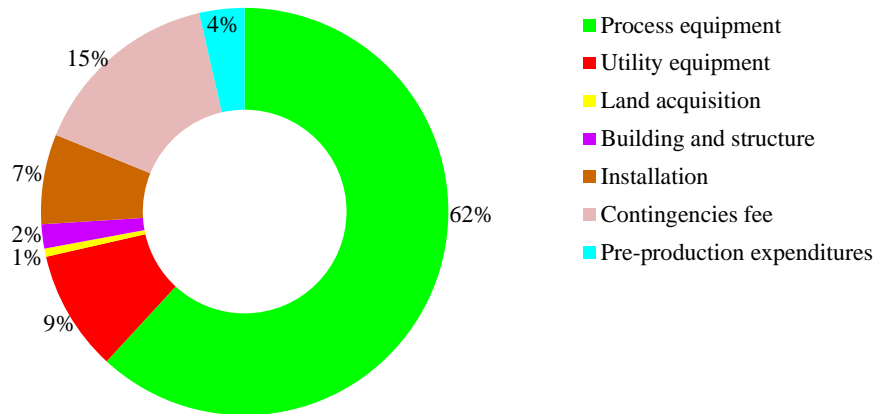


Figure 11: share of different items in total investment costs

Sensitivity analysis

COMFAR III was used for sensitivity analysis. Results indicated that the increase in the internal rate of return had the greatest effect on sales revenues, so that with an increase of 20% in IRR, sales revenues attained 35.57% (Figure 12). Also, it can be seen that the growth in IRR has resulted in a slight increase in fixed assets and led to an extreme decrease in operating costs.

Authors have recently focused on modern technologies to reduce energy consumption, increase efficiency, and use environmentally-friendly reagents. Accordingly, the mechanochemical approach would be a promising technique, due to improving the reaction conditions in lower temperatures and consuming less time. Therefore, one of the main goals of sustainable development can be reached through mechanochemical processes in biodiesel production.

Scope for further research

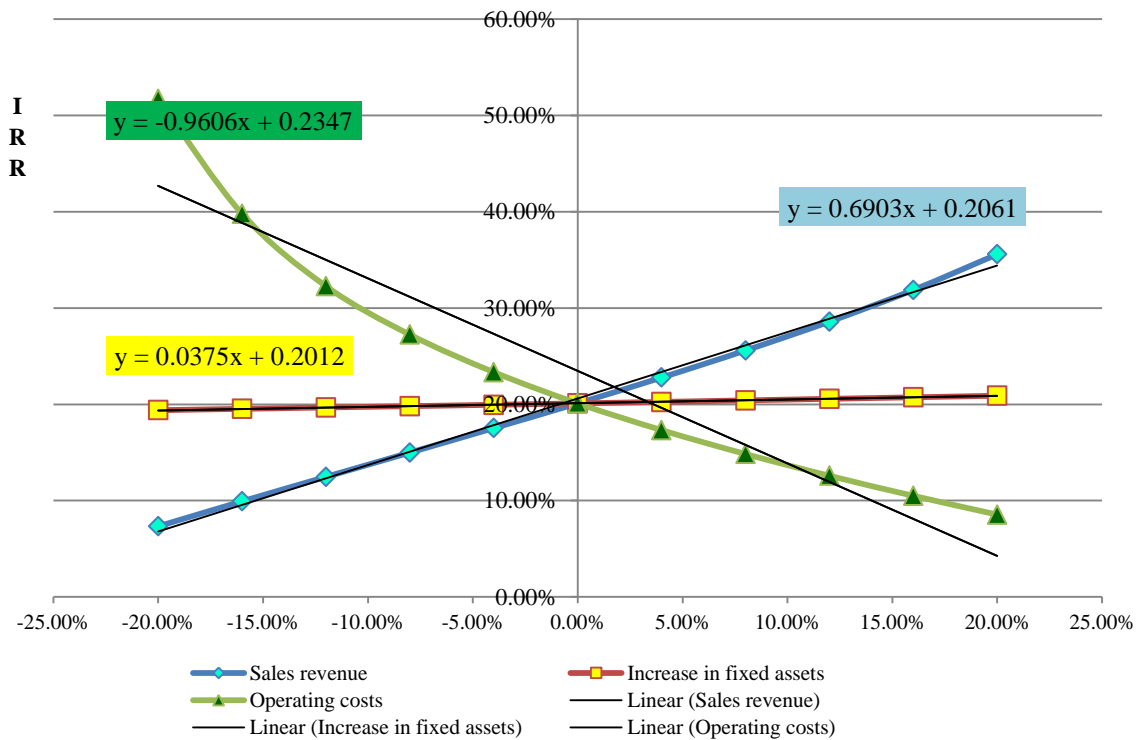


Figure 12: Sensitivity of the IRR on the sales revenue, operating costs and increase in fixed assets

Discussion

In the present study, the production of biodiesel was conducted on laboratory scale, and it was shown that the evaluated properties of the biodiesel conform to the American Society test method standard (ASTM D6751) which is similar to a study conducted by Sadaf, et al.⁵³. From a technical viewpoint, it is noticed that both the density and viscosity of petrodiesel increase when the blends percentage ratio rises; however, energy content of higher-biodiesel-ratio fuel shows an insignificant decrease which can still provide enough energy in engines. On the other hand, the increased cetane index can play a positive role to enhance the quality of burning, which is achieved by adding more biodiesel in petrodiesel. Higher content of biodiesel in conventional fuel improves the quality by decreasing sulfur content and safety parameters, which are flash point and fire point, making it a favorable fuel in harsh conditions. Furthermore, it was evidenced that the improved pour point and cloud point can work positively in cold conditions to keep the fuel from forming wax crystals as can be seen in Atabani et al. investigation⁶⁶.

The ever-increasing greenhouse gas (GHG) rate, which is considered a threat to the environment, is an important issue. In the Iranian national document of the knowledge-based development of renewable energy, biodiesel consumption is a part of the renewable energy domain in the 1404 outlook. One of the macro policies of Iran in the exhibition of bioenergy fuels is the consumption of bioethanol and biodiesel in upcoming years. Also, reducing at least 10 million tons of greenhouse gas emissions in comparison with 2015 is expected by increasing the renewable energy share. Therefore, biofuel, as a prerequisite for economic activities, has become one of the most essential elements in global policies in Iran toward sustainable development. Using WCO as raw material for biodiesel production has been considered not only as a progressive step in reducing environmental pollution, but also as a viable measure to improve human safety^{25,30}.

Conclusion

Due to the growing environmental concerns over

the past years, decisions have been made to achieve sustainable development. While developed countries have made considerable progress in controlling environmental pollution, developing countries (e.g. Iran) are still facing different challenges. Waste cooking oil as a cheaper alternative reduces GHG emissions and prevents waste accumulation¹⁹. Biodiesel blends are beneficial from an environmental perspective to improve the fuel's physicochemical properties; hence, biodiesel blends in Iran have advantages including less consumption of conventional fuel, carbon marketing and reducing environmental pollutants. Moreover, it decreases the dependence on imported oil, due to agricultural development, and creates more occupations in the country, leading to new green policies and sustainable development. The ten percent blend of biodiesel with petrodiesel (B10) improves most of the conventional diesel fuel properties, which can be used without any engine modification. Lowering the amount of sulfur can improve environmental health as a result of using biofuels, to meet one of the fundamental objectives of sustainability.

Economic estimation of factory construction and the IRR sensitivity analysis were conducted on a variety of terms. They indicate that the cost of producing biodiesel in Iran reaches 0.412\$/L. The highest proportion of operating costs respectively belong to WCO (75%) followed by methanol (10%) and machinery, services and maintenance expenses (5%). Moreover, the largest proportion of total investment costs relates to processing equipment (62%), followed by contingencies fees (15%) and utility (9%).

Sensitivity analysis results show that the increase in the IRR has the greatest effect on sales revenue, while the increasing trend in IRR has resulted in a slight increase in fixed assets, and eventually it leads to an extreme decrease in operating costs. Ultimately, the IRR of more than 18% (21.20%) and positive NPV indexes (\$11,722,000) can be concluded that the project would be economically feasible.

Abbreviations

GHG: Green House Gases

B0: 0% Biodiesel + 100% Petrodiesel

B5: 5% Biodiesel + 95% Petrodiesel

B10: 10% Biodiesel + 90% Petrodiesel

B20: 20% Biodiesel + 80% Petrodiesel

B100: 100% Biodiesel + 0% Petrodiesel

WCO: Waste Cooking Oil

PM: Particle Matters

NO_x: Nitrogen Oxides

CO₂: Carbon Dioxide

CO: Carbon Monoxide

HC: Hydro Carbons

LCA: Life Cycle Assessment

Sox: Sulfur Oxides

FAME: Fatty Acid Methyl Ester

FFA: Free Fatty Acid

IRR: Internal Rate Of Return

HHV: Higher Heating Value

IBP: Initial Boiling Point

FBP: Final Boiling Point

NPV: Net Present Value

UNIDO: United Nations Industrial Development Organization

Acknowledgment

The authors would like to thank the University of Tehran Science and Technology Park.

Funding

This research did not receive any specific grant from funding agencies in the public, commercial, or not-for-profit sectors.

Conflict of interest

The authors declare there is no conflict of interest.

This is an Open-Access article distributed in accordance with the terms of the Creative Commons Attribution (CC BY 4.0) license, which permits others to distribute, remix, adapt, and build upon this work for commercial use.

References

1. Song Y, Yang T, Li Z, et al. Research on the direct and indirect effects of environmental regulation on environmental pollution: Empirical evidence from 253 prefecture-level cities in China. *J Clean Prod.* 2020;269:122425.

2. Ahmadi A, Das B, Ehyaei M, et al. Energy, exergy, and techno-economic performance analyses of solar dryers for agro products: A comprehensive review. *Solar Energy.* 2021;228:349-73.
3. Arshad M, Bano I, Khan N, et al. Electricity generation from biogas of poultry waste: An assessment of potential and feasibility in Pakistan. *Renew Sustain Energy Rev.* 2018;81:1241-6.
4. Rahimi M, Catalini G, Hariharan S, et al. Carbon dioxide capture using an electrochemically driven proton concentration process. *Cell Rep Phys Sci.* 2020;1(4):100033.
5. Demirbas A. Biodiesel production from vegetable oils by supercritical methanol. *Journal of Scientific & Industrial Research.* 2005;64(1):858-65.
6. Chang J, Leung DY, Wu C, et al. A review on the energy production, consumption, and prospect of renewable energy in China. *Renew Sustain Energy Rev.* 2003;7(5):453-68.
7. Correa SM, Arbilla G. Carbonyl emissions in diesel and biodiesel exhaust. *Atmos Environ.* 2008;42(4):769-75.
8. Zhang Z, Cheung C, Chan T, et al. Experimental investigation of regulated and unregulated emissions from a diesel engine fueled with Euro V diesel fuel and fumigation methanol. *Atmos Environ.* 2010;44(8):1054-61.
9. Okona-Mensah K, Battershill J, Boobis A, et al. An approach to investigating the importance of high potency polycyclic aromatic hydrocarbons (PAHs) in the induction of lung cancer by air pollution. *Food Chem Toxicol.* 2005;43(7):1103-16.
10. Borugadda VB, Paul AK, Chaudhari AJ, et al. Influence of waste cooking oil methyl ester biodiesel blends on the performance and emissions of a diesel engine. *Waste Biomass Valorization.* 2018;9:283-92.
11. Lin YC, Hsu KH, Chen CB. Experimental investigation of the performance and emissions of a heavy-duty diesel engine fueled with waste cooking oil biodiesel/ultra-low sulfur diesel blends. *Energy.* 2011;36(1):241-8.
12. Nisar N, Mehmood S, Nisar H, et al. Brassicaceae family oil methyl esters blended

- with ultra-low sulphur diesel fuel (ULSD): Comparison of fuel properties with fuel standards. *Renew Energy*. 2018;117:393-403.
13. Dhawane SH, Karmakar B, Ghosh S, et al. Parametric optimisation of biodiesel synthesis from waste cooking oil via Taguchi approach. *J Environ Chem Eng*. 2018;6(4):3971-80.
 14. Cholapandian K, Gurunathan B, Rajendran N. Investigation of CaO nanocatalyst synthesized from *Acalypha indica* leaves and its application in biodiesel production using waste cooking oil. *Fuel*. 2022;312:122958.
 15. Oh PP, Lau HLN, Chen J, et al. A review on conventional technologies and emerging process intensification (PI) methods for biodiesel production. *Renew Sustain Energy Rev*. 2012;16(7):5131-45.
 16. Atapour M, Kariminia HR, Moslehabadi PM. Optimization of biodiesel production by alkali-catalyzed transesterification of used frying oil. *Process Saf Environ Prot*. 2014;92(2):179-85.
 17. Bashiri H, Pourbeiram N. Biodiesel production through transesterification of soybean oil: A kinetic Monte Carlo study. *J Mol Liq*. 2016;223:10-5.
 18. Silitonga A, Masjuki H, Mahlia T, et al. Overview properties of biodiesel diesel blends from edible and non-edible feedstock. *Renew Sustain Energy Rev*. 2013;22:346-60.
 19. Can Ö. Combustion characteristics, performance and exhaust emissions of a diesel engine fueled with a waste cooking oil biodiesel mixture. *Energy Convers Manag*. 2014;87:676-86.
 20. Venkanna B, Venkataramana Reddy C. Direct injection diesel engine performance, emission, and combustion characteristics using diesel fuel, nonedible honne oil methyl ester, and blends with diesel fuel. *Int J Energy Res*. 2012;36(13):1247-61.
 21. Moon G, Lee Y, Choi K, et al. Emission characteristics of diesel, gas to liquid, and biodiesel-blended fuels in a diesel engine for passenger cars. *Fuel*. 2010;89(12):3840-6.
 22. Habibullah M, Masjuki H, Kalam M, et al. Biodiesel production and performance evaluation of coconut, palm and their combined blend with diesel in a single-cylinder diesel engine. *Energy Convers Manag*. 2014;87:250-7.
 23. Sahoo P, Das L. Process optimization for biodiesel production from *Jatropha*, *Karanja* and *Polanga* oils. *Fuel*. 2009;88(9):1588-94.
 24. Nabi MN, Rahman MM, Akhter MS. Biodiesel from cotton seed oil and its effect on engine performance and exhaust emissions. *Appl Therm Eng*. 2009;29(11):2265-70.
 25. Ghanei R. Improving cold-flow properties of biodiesel through blending with nonedible castor oil methyl ester. *Environ Prog Sustain Energy*. 2015;34(3):897-902.
 26. Chavan SB, Yadav M, Singh R, et al. Production of biodiesel from three indigenous feedstock: Optimization of process parameters and assessment of various fuel properties. *Environ Prog Sustain Energy*. 2017;36(3):788-95.
 27. Abedin M, Masjuki H, Kalam M, et al. Performance, emissions, and heat losses of palm and *jatropha* biodiesel blends in a diesel engine. *Ind Crops Prod*. 2014;59:96-104.
 28. Capodaglio AG, Callegari A. Feedstock and process influence on biodiesel produced from waste sewage sludge. *J Environ Manage*. 2017;216:176-82.
 29. Moecke EHS, Feller R, Dos Santos HA, et al. Biodiesel production from waste cooking oil for use as fuel in artisanal fishing boats: Integrating environmental, economic and social aspects. *J Clean Prod*. 2016;135:679-88.
 30. De Pontes Souza D, Mendonça FM, Alves Nunes KR, et al. Environmental and socioeconomic analysis of producing biodiesel from used cooking oil in Rio de Janeiro. *J Ind Ecol*. 2012;16(4):655-64.
 31. Passell H, Dhaliwal H, Reno M, et al. Algae biodiesel life cycle assessment using current commercial data. *J Environ Manage*. 2013;129:103-11.
 32. Taghizadeh-Alisarai A, Hosseini SH, Ghobadian B, et al. Biofuel production from citrus wastes: A feasibility study in Iran. *Renew Sustain Energy Rev*. 2017;69:1100-12.
 33. Hajjari M, Tabatabaei M, Aghbashlo M, et al. A review on the prospects of sustainable biodiesel

- production: A global scenario with an emphasis on waste-oil biodiesel utilization. *Renew Sustain Energy Rev.* 2017;72:445-64.
34. Zahed MA, Zakeralhosseini Z, Mohajeri L, et al. Multivariable analysis and optimization of biodiesel production from waste cooking oil. *Environmental Processes.* 2018;5(2):303-12.
 35. Salehi A, Karbassi A, Ghobadian B, et al. Simulation process of biodiesel production plant. *Environ Prog Sustain Energy.* 2019;38(6): e13264.
 36. Cao Y, Doustgani A, Salehi A, et al. The economic evaluation of establishing a plant for producing biodiesel from edible oil wastes in oil-rich countries: case study Iran. *Energy.* 2020;213:118760.
 37. Feng L, Liu J, Lu H, et al. Techno-economic and profitability analysis of plant for producing biodiesel from fresh vegetable oil and waste frying oil on large-scale. *Fuel.* 2022;323:124304.
 38. Ghobadian B. Liquid biofuels potential and outlook in Iran. *Renew Sustain Energy Rev.* 2012;16(7):4379-84.
 39. Statista. Largest producers of CO2 emissions worldwide in 2016 based on their share of global CO2 emissions. Available from: <https://www.statista.com/statistics/271748/the-largest-emitters-of-co2-in-the-world>. [Cited 10 September 2016]
 40. Emissions GC. Available from: <https://www.co2.earth/global-co2emissions>. [Cited 20 November 2016]
 41. Mathimani T, Kumar TS, Chandrasekar M, et al. Assessment of fuel properties, engine performance and emission characteristics of outdoor grown marine *Chlorella vulgaris* BDUG 91771 biodiesel. *Renew Energy.* 2017;105:637-46.
 42. Karmakar A, Karmakar S, Mukherjee S. Properties of various plants and animals feedstocks for biodiesel production. *Bioresour Technol.* 2010;101(19):7201-10.
 43. Singh A, He B, Thompson J, et al. Process optimization of biodiesel production using alkaline catalysts. *Appl Eng Agric.* 2006;22(4):597-600.
 44. Al-Sakkari EG, Elozeiri AA, Abdeldayem OM, et al. Fish and animal waste as catalysts for biodiesel synthesis. *Waste and Biodiesel.* 2022:119-36.
 45. Dharma S, Masjuki H, Ong HC, et al. Optimization of biodiesel production process for mixed *Jatropha curcas*-*Ceiba pentandra* biodiesel using response surface methodology. *Energy Convers Manag.* 2016;115:178-90.
 46. Moser BR, Vaughn SF. Biodiesel from corn distillers dried grains with solubles: preparation, evaluation, and properties. *Bioenergy Res.* 2012;5(2):439-49.
 47. Hayyan A, Hashim MA, Hayyan M. Application of a novel catalyst in the esterification of mixed industrial palm oil for biodiesel production. *Bioenergy Res.* 2015;8(1):459-63.
 48. Wakil M, Kalam M, Masjuki H, et al. Influence of biodiesel blending on physicochemical properties and importance of mathematical model for predicting the properties of biodiesel blend. *Energy Convers Manag.* 2015;94:51-67.
 49. Chauhan BS, Singh RK, Cho H, et al. Practice of diesel fuel blends using alternative fuels: A review. *Renew Sustain Energy Rev.* 2016;59:1358-68.
 50. Yilmaz N, Vigil FM, Benalil K, et al. Effect of biodiesel-butanol fuel blends on emissions and performance characteristics of a diesel engine. *Fuel.* 2014;135:46-50.
 51. Al-Hamamre Z, Al-Salaymeh A. Physical properties of (jojoba oil+ biodiesel), (jojoba oil+ diesel) and (biodiesel+ diesel) blends. *Fuel.* 2014;123:175-88.
 52. Phan AN, Phan TM. Biodiesel production from waste cooking oils. *Fuel.* 2008;87(17-18):3490-6.
 53. Sadaf S, Iqbal J, Ullah I, et al. Biodiesel production from waste cooking oil: an efficient technique to convert waste into biodiesel. *Sustain Cities Soc.* 2018;41:220-6.
 54. Saxena P, Jawale S, Joshipura MH. A review on prediction of properties of biodiesel and blends of biodiesel. *Procedia Eng.* 2013;51:395-402.
 55. Ryan III T, Dodge L, Callahan T. The effects of vegetable oil properties on injection and

- combustion in two different diesel engines. *J Am Oil Chem Soc.* 1984;61(10):1610-9.
56. Hassan N, Rasul M, Harch CA. Modelling and experimental investigation of engine performance and emissions fuelled with biodiesel produced from Australian beauty leaf tree. *Fuel.* 2015;150:625-35.
57. Atabani A, Silitonga A, Ong H, et al. Non-edible vegetable oils: a critical evaluation of oil extraction, fatty acid compositions, biodiesel production, characteristics, engine performance and emissions production. *Renew Sustain Energy Rev.* 2013;18:211-45.
58. Sbihi HM, Nehdi IA, Tan CP, et al. Production and characterization of biodiesel from *Camelus dromedarius* (Hachi) fat. *Energy Convers Manag.* 2014;78:50-7.
59. Azad A, Uddin SA, Alam M. Experimental study of DI diesel engine performance using biodiesel blends with kerosene. *International Journal of Energy and Environment.* 2013;4(2):265-78.
60. Moser BR. Biodiesel production, properties, and feedstocks. *In Vitro Cell Dev Biol Plant.* 2009;45(3):229-66.
61. Usta N. An experimental study on performance and exhaust emissions of a diesel engine fuelled with tobacco seed oil methyl ester. *Energy Convers Manag.* 2005;46(15):2373-86.
62. Bi C-h, Min M, Nie Y, et al. Process development for scum to biodiesel conversion. *Bioresour Technol.* 2015;185:185-93.
63. Azad A, Ameer Uddin S. Performance study of a diesel engine by first generation bio-fuel blends with fossil fuel: An experimental study. *J Renew Sustain Energy.* 2013;5(1):013118.
64. Acharya N, Nanda P, Panda S, et al. Analysis of properties and estimation of optimum blending ratio of blended mahua biodiesel. *Engineering Science and Technology, an International Journal.* 2017;20(2):511-7.
65. Hasan M, Rahman M. Performance and emission characteristics of biodiesel–diesel blend and environmental and economic impacts of biodiesel production: A review. *Renew Sustain Energy Rev.* 2017;74:938-48.
66. Atabani AE, Silitonga AS, Badruddin IA, et al. A comprehensive review on biodiesel as an alternative energy resource and its characteristics. *Renew Sustain Energy Rev.* 2012;16(4):2070-93.
67. Phan AN, Phan TM. Biodiesel production from waste cooking oils. *Fuel.* 2008;87(17):3490-6.
68. Ferris AM, Rothamer DA. Methodology for the experimental measurement of vapor–liquid equilibrium distillation curves using a modified ASTM D86 setup. *Fuel.* 2016;182:467-79.
69. Mohammadshirazi A, Akram A, Rafiee S, et al. Energy and cost analyses of biodiesel production from waste cooking oil. *Renew Sustain Energy Rev.* 2014;33:44-9